

Paper Titles

Effect of Shielding Gas Mixture on Gas Metal Arc Welding (GMAW) of Low Carbon Steel (LR Grade A)

908



Abstract:

The aimed of this research is to determine the feasibility and effect of the mixture of the shielding gas in the physical and mechanical properties. Low carbon steel LR grade A in a thickness 12 mm were joined in butt joint types using GMAW (Gas Metal Arc Welding) with groove's gap 5 mm and groove angle's 40° with variation of shielding gas composition. The composition of shielding gas that used were 100% Ar, 100 % CO₂ and 50% Ar + 50 % CO₂. The measured of mechanical properties with regard to strength, hardness and toughness using, tensile test, bending test, Vickers hardness Test, and Charpy impact test respectively. The physical properties examined with optical microscope. Results show that tensile strength of welding metals are higher than raw materials. Welds metal with mixing Ar + CO shielding gas has the highest tensile strength. Hardness of weld metals with the shielding gas 100% Ar, 100 % CO₂ and 50% Ar + 50 % CO₂ are 244.9; 209.4; and 209.4 VHN respectively. The temperature of Charpy test was varied to find the transition temperature of the materials. The temperature that used were -60°C, -40°C, -20°C, 0°C, 20°C , and room temperature. Weld metals with various shielding gas have similar trends of toughness flux that was corellated with the microstructure of weld .

Access through your institution

ADD TO CART

Info:

Periodical:

[Key Engineering Materials](#) (Volume 705)

Edited by:	Alexander M. Korsunsky, Chobin Makabe, Prof. Haider F. Abdul Amir and Tjokorda Gde Tirta Nindhia
Pages:	250-254
DOI:	https://doi.org/10.4028/www.scientific.net/KEM.705.250
Citation:	Cite this paper
Online since:	August 2016
Authors:	Yustiasih Purwaningrum* , Triyono , M. Wirawan Pu , Fandi Alfarizi
Keywords:	GMAW , Shielding Gas , Tensile Strength , Toughness
Export:	RIS , BibTeX
Price:	39,00 €
Permissions:	Request Permissions
Share:	

* - Corresponding Author

References

Cited by

Related Articles

DISTRIBUTION & ACCESS

FOR PUBLICATION

INSIGHTS

DOWNLOADS

ABOUT US

POLICY & ETHICS

CONTACT US

IMPRINT

[PRIVACY POLICY](#)

[SITEMAP](#)

[ALL CONFERENCES](#)

[ALL SPECIAL ISSUES](#)

[ALL NEWS](#)

Scientific.Net is a registered brand of Trans Tech Publications Ltd

© 2022 by Trans Tech Publications Ltd. All Rights Reserved

Search

Journals

Engineering Research

Advanced Engineering Forum

Applied Mechanics and Materials

Engineering Innovations

Journal of Biomimetics, Biomaterials and Biomedical Engineering

International Journal of Engineering Research in Africa

Materials Science

Advanced Materials Research

Defect and Diffusion Forum

Diffusion Foundations and Materials Applications

Journal of Metastable and Nanocrystalline Materials

Journal of Nano Research

Key Engineering Materials

Materials Science Forum

Nano Hybrids and Composites

Solid State Phenomena

Engineering Series

Advances in Science and Technology

Construction Technologies and Architecture

Books

Special Book Collections

Foundations of Materials Science and Engineering

Scientific Books Collection

Specialized Collections

Retrospective Collection

Key Engineering Materials - Editorial Board

ISSN: 1662-9795

Details

Volumes

Editorial Board

Founding Editor

Fred H. Wohlbiert

Editor(s) in Chief

Assoc. Prof. Dr. Cecilia Poletti

ORCID

Graz University of Technology, Institute of Materials Science, Joining and Forming; Kopernikusgasse 24/1,
Graz, A-8010, Austria;

Prof. Dr. José Manuel Torralba

[ORCID](#)

Universidad Carlos III de Madrid, IMDEA Materials; Av. Universidad 30, Leganés, 28911, Spain;

Editorial Board

Prof. Aldo Roberto Boccaccini

University of Erlangen-Nürnberg, Institute of Biomaterials, Department of Materials Science and Engineering; Cauerstrasse 6, Erlangen, 91058, Germany;

Prof. Mónica Campos

[ORCID](#)

University Carlos III de Madrid, Department of Materials Science and Engineering; Av. Universidad 30, Leganés-Madrid, 28911, Spain;

Dr. Li Chang

University of Sydney, School of Aerospace, Mechanical and Mechatronic Engineering; Sydney, Australia, 2006;

Prof. Yi Bing Cheng

[ORCID](#)

Monash University, Department of Materials Science and Engineering; PO Box 197, Caulfield East, Australia, 3145;

Prof. Ilaria Cristofolini

[ORCID](#)

University of Trento, Department of Industrial Engineering; Via Sommarive 9, Povo, 38123, Italy;

Prof. Robert Danzer

Montanuniversität Leoben, Institut für Struktur- und Funktionskeramik; Peter-Tunner-Strasse 5, Leoben, A-8700, Austria;

Prof. Suong Van Hoa

Concordia University, Department of Mechanical and Industrial Engineering; 1455 Demaisonneuve West # EV 4-145, Montreal, Canada, H3G1M8;

Prof. Xiao Zhi Hu

University of Western Australia, School of Mechanical and Chemical Engineering; Perth, Australia, WA 6009;

Prof. Mohamed A. Taha

Ain-Shms University, Department of Design and Production Engineering, Faculty of Engineering; Khalifa El-Maamon st, Abbasiya sq., Cairo, Egypt, 11566;

Prof. Alejandro Ureña Fernandez

Universidad Rey Juan Carlos (URJC), Department of Materials Science and Engineering; Tulipan s/n
28933, Mostoles, Madrid, Spain;

Prof. Dragan P. Uskokovic

Institute of Technical Sciences of the Serbian Academy of Sciences and Arts; Knez Mihailova 35/IV,
Belgrade, Serbia;

Prof. Maria Teresa Vieira

ORCID

Universidade de Coimbra, ICEMS - Instituto de Ciência e Engenharia de Materiais e Superfícies ; Pólo II-
Pinhal de Marrocos, Coimbra, 3030-788, Portugal;

Prof. Zhi Rui Wang

University of Toronto, Department of Materials Science and Engineering; 184 College Street, Toronto,
Canada, M5S 3E4;

Prof. Ming Xing Zhang

University of Queensland, School of Mechanical and Mining Engineering; St. Lucia, Queensland,
Australia, QLD 4072;

[DISTRIBUTION & ACCESS](#)

[FOR PUBLICATION](#)

[INSIGHTS](#)

[DOWNLOADS](#)

[ABOUT US](#)

[POLICY & ETHICS](#)

[CONTACT US](#)

[IMPRINT](#)

[PRIVACY POLICY](#)

[SITEMAP](#)

[ALL CONFERENCES](#)

[ALL SPECIAL ISSUES](#)

[ALL NEWS](#)

Volumes

Key Engineering Materials Vol. 705

DOI: <https://doi.org/10.4028/www.scientific.net/KEM.705>ToC: [Table of Contents](#)

<<	<	...	3	4	5	6	7	>
----	---	-----	---	---	----------	---	---	---

Paper Title	Page
<u>Thermodynamic Study on Interfacial Reaction between Molten Iron and Spinel</u>	219
Authors: Hirohide Okuno, Naotaka Fukami, Nobuya Shinozaki Abstract: The effect of the oxygen concentration in the molten iron on the formation of the FeO-MgO phase at the interface between the ...more	
<u>Comparative Study of Drilling Induced Delamination in CFRP with Different Ply Orientation</u>	227
Authors: Kamlesh Phapale, Sandip Patil, Ramesh Singh, R.K.P. Singh Abstract: Composite laminates are used in many applications in industries like aerospace and aircraft due to their extremely high ...more	
<u>Effect of Gas Based Coolant Lubricants on Machinability of Titanium Alloy Ti6Al4V</u>	233

Authors: Sandip Patil, Pravin Pawar, Swapnil Kekade, Sachin Patil, Kiran Gujar, R.K.P. Singh

Abstract: Machining of titanium alloys generates enormous amount of heat at the chip-tool interface leading to poor machinability. Use of [...more](#)

Investigation of Microstructure in Friction Stir Welded Al-Cu-Li Alloy

240

Authors: Ye Rim Lee, Kookil No, Jong Hoon Yoon, Joon Tae Yoo, Ho Sung Lee

Abstract: It is well known that the addition of Li to aluminum alloys offers an attractive combination of low density and high modulus, [...more](#)

Methodology of Uniform Filling Control for Vacuum Casting

245

Authors: Fei Long Mao, Hai Guang Zhang, Qing Xi Hu

Abstract: Aiming at solving the problem that results from flow instability two-component materials, uneven density and thus affects [...more](#)

Effect of Shielding Gas Mixture on Gas Metal Arc Welding (GMAW) of Low Carbon Steel (LR Grade A)

250

Authors: Yustiasih Purwaningrum, Triyono, M. Wirawan Pu, Fandi Alfarizi

Abstract: The aimed of this research is to determine the feasibility and effect of the mixture of the shielding gas in the physical and [...more](#)

Parametric Analysis of Cylindrical Plunge Grinding on Micro-Alloyed Steel Using Taguchi Analysis

255

Authors: Swapnil Kekade, Sandip Patil, Suhas Joshi, Rajkumar Singh

Abstract: In the automotive industry, grinding of round diameters is an important process, to achieve desired tolerances and finish. While the [...more](#)

Time Dependent High Dimension Model of Functional Gradient Thermal Barrier Coating Material

263

Authors: Chen Zhao, Yu Guang Li, She Sheng Zhang

Abstract: A high dimension time dependent model of designing functional gradient thermal barrier coating material is built by using [...more](#)

Hydrophobicity of Surfaces Coated with Functionalized Titanium Dioxide Nanoparticles

268

Authors: Paul Albert L. Sino, Marvin U. Herrera, Mary Donnabelle L. Balela

Abstract: Hydrophobic surfaces are eyed for their self-cleaning ability because water droplets can roll on them (instead of clinging), thus the [...more](#)

Butane/Propane Gas Sensing Using Zinc Oxide Film Grown by Successive Ionic Layer Adhesion and Reaction

273

Authors: Emmanuel A. Florido, Sarah Allyssa Solidum

Abstract: This study was aimed to test the ability of zinc oxide (ZnO) film fabricated by successive ionic layer adsorption and reaction [...more](#)

Showing 41 to 50 of 68 Paper Titles

<<	<	...	3	4	5	6	7	>
----	---	-----	---	---	----------	---	---	---

DISTRIBUTION & ACCESS

FOR PUBLICATION

INSIGHTS

DOWNLOADS

ABOUT US

POLICY & ETHICS

CONTACT US

IMPRINT

PRIVACY POLICY

SITEMAP

ALL CONFERENCES

ALL SPECIAL ISSUES

ALL NEWS

Effect of Shielding Gas Mixture on Gas Metal Arc Welding (GMAW) of Low Carbon Steel (LR Grade A)

Yustiasih Purwaningrum^{1,a*}, Triyono², M. Wirawan PU^{1,a}, Fandi Alfarizi^{1,a}

¹ Mechanical Engineering Department, Islamic University of Indonesia
Yogyakarta, Indonesia

² Mechanical Engineering Department, Sebelas Maret University
Surakarta, Indonesia

^ayustiasih.purwaningrum@uii.ac.id/yustiasih2003@yahoo.co.nz, ^btriyono@uns.ac.id

Keywords: GMAW, Shielding Gas, Tensile strength, Toughness

Abstract. The aimed of this research is to determine the feasibility and effect of the mixture of the shielding gas in the physical and mechanical properties. Low carbon steel LR grade A in a thickness 12 mm were joined in butt joint types using GMAW (Gas Metal Arc Welding) with groove's gap 5 mm and groove angle's 40° with variation of shielding gas composition. The composition of shielding gas that used were 100% Ar, 100 % CO₂ and 50% Ar + 50 % CO₂. The measured of mechanical properties with regard to strength, hardness and toughness using, tensile test, bending test, Vickers hardness Test, and Charpy impact test respectively. The physical properties examined with optical microscope. Results show that tensile strength of welding metals are higher than raw materials. Welds metal with mixing Ar + CO shielding gas has the highest tensile strength. Hardness of weld metals with the shielding gas 100% Ar, 100 % CO₂ and 50% Ar + 50 % CO₂ are 244.9; 209.4; and 209.4 VHN respectively. The temperature of Charpy test was varied to find the transition temperature of the materials. The temperature that used were -60°C, -40°C, -20°C, 0°C, 20°C, and room temperature. Weld metals with various shielding gas have similar trends of toughness flux that was corellated with the microstructure of weld .

Introduction

The Study for The Maritime Traffic Safety System Development Plan reports that in the year 2007-2011 the percentage of the factors causing the sea accident caused by technical factors is 59%. These data indicate the weld joint is the most critical part of including a structure so that researchers and practitioners should pay greater attention on the part of the weld joint.

There are four mechanisms that lead to the failure of the ship's structure, that yield due to tensile or pressure, buckling due to shear instability, fatigue cracking and brittle fracture. According to German Standard DIN 8528 (1975) weldability properties are composed of three elements, that welding suitability of materials, welding reliability of design, and welding in manufacturing feasibility.

The shielding gas used for GMAW process has to protect the weld pool and molten droplet transferred across the arc. Carbon dioxide (CO₂) generally used as a shielding gas due to its cheapness, but it use has been limited because of the problem of poor all position performance, spatter and oxidation losses [1]. On the other hand Argon (Ar) cannot obtained the desired bead characteristic and arc stability [2]. Therefore, argon mixed with CO₂ is being preferred as a shielding gas for weld bead characteristics, inclusions distribution arc stability, and mode of metal transfer. The use of different shielding gas produces corrosion resistance and hardness values are different [3]. The composition of shielding gas and filler wire in GMAW of HSLA steels determines inclusion characteristic, microstructures, and mechanical properties [4].

Material and Welding Experimentals

Materials

The steel sheet used was LR Grade A steel plate with a thickness of 12 mm. The steel sheet that has been provided measuring 600 mm x 300 mm, can be seen in Figure 1. The chemical compositions of test materials are shown in Table 1.



Fig. 1 Steel Sheet Grade A

Table 1. Chemical Composition of LR Steel (BKI, 2013)

Grade	C max	Mn min	Si Max	P Max	S Max	Al Min
A	0.21	2.5 x C	0.50	0.035	0.035	-
B	0.21	0.80	0.35	0.035	0.035	-
C	0.21	0.60	0.35	0.035	0.035	0.015
D	0.20	0.70	0.35	0.035	0.035	0.015

Welding Processes

The welding process was multilayer one side welding, the parameters of weld are shown in Table 2. Welding processes used Butt joint types using GMAW (Gas Metal Arc Welding) with groove's gap 5 mm and groove angle's 40° with variation of shielding gas mixture. The composition of shielding gas that used were 100% Ar, 100 % CO₂ and 50% Ar + 50 % CO₂.

Table 2. Parameters of Welding

No	Wire Rate (mm/s)	Welding Rate (mm/s)	Voltage (Volt)	Gas Rate (liter/menit)
1	100,43	6,25	22	15
2	100,43	6,25	23	15
3	100,43	6,25	24	15
4	100,43	6,25	25	15
5	100,43	6,25	26	15
6	100,43	6,25	23	15
7	100,43	6,25	24	15
8	100,43	5,56	23	15
9	100,43	3,16	23	15
10	100,43	3,16	24	15
11	135,58	5,56	23	15
12	172,41	5,56	23	15

Joints Characterizations

Mechanical strength of weld metals were performed by tensile testing ,impact toughness testing and bend testing. Charpy Impact testing is used to determine the value of the toughness of welds. Temperature impact testing is used at -60°C, -40°C, -20°C, 0°C, 20°C, and 30°C. Liquid nitrogen is used to get the temperature < 0°C.

The impact specimens refered to ASTM E23-96 as seen in fig.2. The Vickers hardness measurements across the base metal, HAZ (heat affected zone), and the weld metal. Standard metallographic procedure ASTM E3-01 used to prepared metallography specimens. The microstructure of mild steel was revealed by using HNO₃ 2.5%

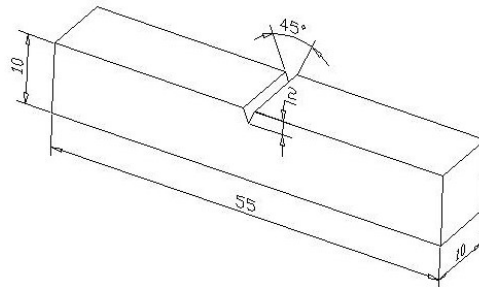


Fig. 2 Impact Test Specimen (ASTM E23-96) [5]

Results and Discussions

As we can see from Fig. 3 the shielding gas influence on microstructure of material of welding joint. The most homogeneous structure is received, using shielding gas Argon (Fig. 3 a). It is evident that an increase in CO₂ content in the shielding gas increases the grain size. This microstructure was formed due to the high welding heat during welding process.

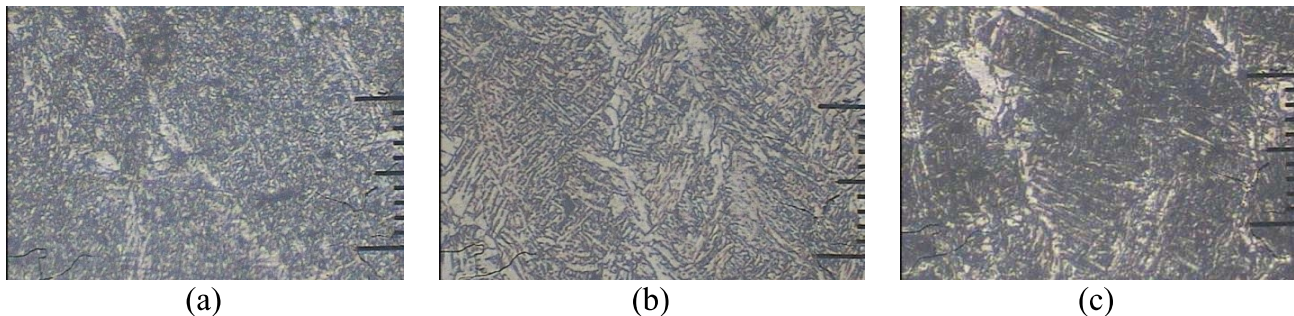


Fig. 3 Microstructure of Welding Metals
(a) Argon (b) Argon + CO₂ (c) CO₂

The tensile strength of the GMAW joints are shown in Figure 4. During tensile test, all welded specimens exhibited fracture at base metals (Fig 5). The tensile strength of welding materials are higher than raw material.

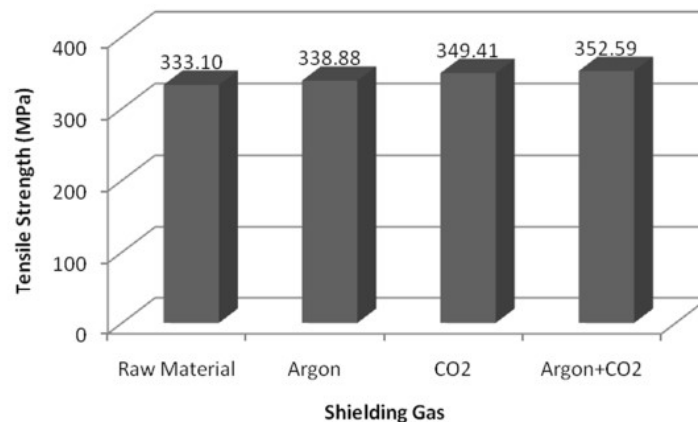


Fig. 4 Effect of Shielding Gas on Tensile Strength

Bending tests using the face transverse bending. The use of this method aims to look at the strength of the weld surface tensile and compressive stress. Another objects of bending test is to see the cracks that appear in the welding structure.

Criteria for bending test according to ASME IX 2010 is as follows:

1. Cracks size in the area of weld metal and HAZ does not exceed 1/8 inch (± 3.0 mm) were measured from all directions surface.
2. Maximum crack size in the welding area is 1.6 mm.

The results of bending test shown at figure 5 and the bending specimens shown at figure 6. Test results shows that the value of the bending strength of the raw material has the highest value is 632.33 Mpa. The lowest value of bending strength is welding metals with shielding gas argon gas which has a value 17.5% lower than the base metal.

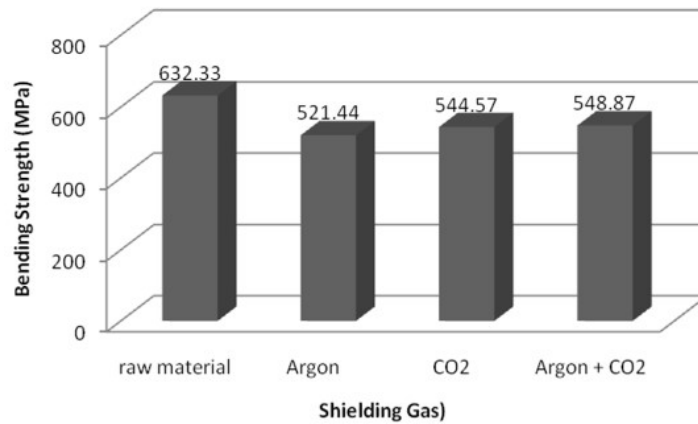


Fig. 5 Effect of Shielding Gas on Bending Strength


In Figure 6 is shown that all the specimens are eligible to qualify in the bending test, because there is no defects in welding and welding quality can be said to be good.



Fig. 6 Specimens of Bending Test

Transition temperature is the temperature at which the material properties change from brittle to ductile. At temperatures below the transition temperature, the weld metal has a brittle properties while at temperatures above the transition temperature of the metal having ductile properties. The lower the transition temperature, the better the toughness of metals.

Figure 7 shows that the transition temperatures are at temperatures between -20°C to 0°C . Welding joints can be used for construction if the value of the absorbed energy at a temperature -50°C is 30 J and at the temperature 0°C is 100 J [6].

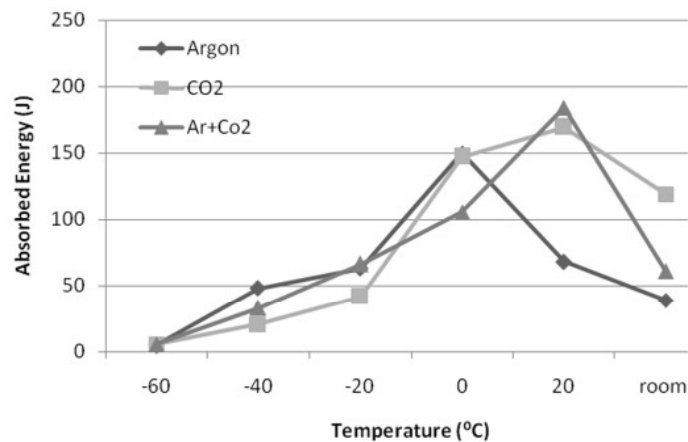

The hardness of weld metal given in Fig 8. The highest hardness numbers found on the weld metals with shielding gas Argon.

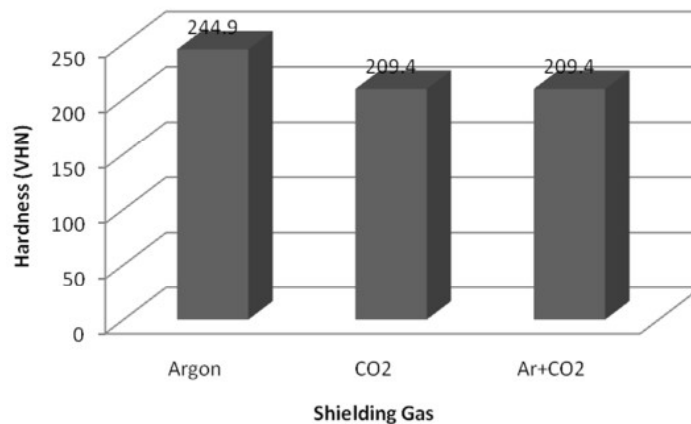


Fig. 8 Effect of Shielding Gas on Hardness

Conclusions

The main results are summarized as follows:

1. An increase in CO₂ content in the shielding gas increases the grain size of microstructure.
2. That tensile strength of welding metals with variation of shielding gas are higher than raw materials.
3. The transition temperatures of weld metals are at temperatures between -20°C to 0°C.
4. Welded joints can be used for construction because eligible absorbed energy value.

Acknowledgment

The authors would like to express their sincere gratitude for the financial support of the DIKTI (Hibah Bersaing) with Contract No.029/Dir/DPPM/70/Hibah Bersaing-Lanjutan DIKTI/III/2015

References

- [1] T. Varga, T. Konkoly, and H. Straube, Investigation on microstructure, toughness and defect tolerance of gas metal arc welding, 1990, *IIW Document X1205-90*
- [2] V.V. Vaidya, Shielding gas mixture for semiautomatic welds, *Welding Journal*, 1996, 81, 43-48
- [3] S. Mukhopadhyay, and T.K. Pal, Effect of shielding gas mixture on gas metal arc welding of HSLA steel using solid and flux-cored wires, *International Journal of Advanced Manufacturing Technology*, 2006, 29:262-268
- [4] P. Sas, Vibration testing: state of the art and challenges, in: M.D. Gilchrist (Ed.), *Modern Practice in Stress and Vibration Analysis*, A.A. Balkema, Rotterdam, 1997, pp.65-74.
- [5] S. Liu, Metallography of HSLA Steel Weldments Engineering Materials, Volume 69 and 70 pp. 1-20
- [6] MQ. Johnsons, GM. Evans, and GR. Edwards, The influences of addition and interpass temperatur on the microstructures and mechanical properties of high strength SMA weld metals, *ISIJ International* .1985,vol 35 No. 10, pp 1222-1231, 1985